

<b>Province:</b> Saskatchewan	<b>Materials:</b> Asphalt Cements
<b>Date Last Reviewed:</b> July 15, 2025	<b>Web Address:</b> <a href="http://www.highways.gov.sk.ca/business">http://www.highways.gov.sk.ca/business</a>
<b>Materials Engineer:</b> Aziz Salifu & Kelly Pederson	<b>Contact Info:</b> <a href="mailto:aziz.salifu@gov.sk.ca">aziz.salifu@gov.sk.ca</a> ; & <a href="mailto:kelly.pederson@gov.sk.ca">kelly.pederson@gov.sk.ca</a>


Asphalt Binder		
	Description	Asphalt Cement
	PMA's	N/A
	Exclusions	Supplier prequalification required.

Saskatchewan		Table 1: PG Requirements for Penetration-Graded Asphalt Binders							
Property		Test Method: AASTHO (T), ASTM (D) or other	Requirements by Penetration Grade						
			150- 200(A)	200- 300(A)	300- 400(A)	400- 500(A)	200- 300(B)	300- 400(B)	
<b>ORIGINAL</b>									
Flash Point, ° C		ASTM D92	205 min.	175 min.	175 min.	175 min.	175 min.	175 min.	
Penetration, 100g, 5s, tenths of mm		25 °C ASTM D5	Note (1)	Note (1)	Note (1)	Note (1)	Note (1)	Note (1)	
Viscosity	Group	60 °C Note (1)	Note (1)	Note (1)	Note (1)	Note (1)	Note (1)	Note(1)	
	A								
	B								
	C								
Ductility, cm		15 °C	ASTM D113	-	100 min.	100 min.	-	100 min.	-
		25 °C	ASTM D113	100 min.	-	-	-	-	-
Solubility in Trichloroethylene, % by mass		ASTM D2042	99.5 min.	99.5 min.	99.5 min.	99.5 min.	99.5 min.	99.5 min.	
<b>TFO RESIDUE</b>									
Mass Loss, %		ASTM D1754	1.0 max.	1.5 max.	2.0 max.	2.5 max.	1.5 max.	2.0 max.	
Penetration, 100g, 5s, % of original, %		25 °C ASTM D5	50 min.	45 min.	-	-	45 min.	-	
Viscosity of residue, % of original, %		60 °C ASTM D2171	-	-	300 max.	400 max.	-	300 max.	
<b>NOTES</b>		1. Viscosity @ 60C and penetration @ 25C shall fall within the area described in Figure 1.							

Disclaimer: "To ensure the most accurate and current information, the specific agency should be contacted."



**FIGURE 1 | Penetration-Absolute Viscosity Relationships for Asphalt Cements**

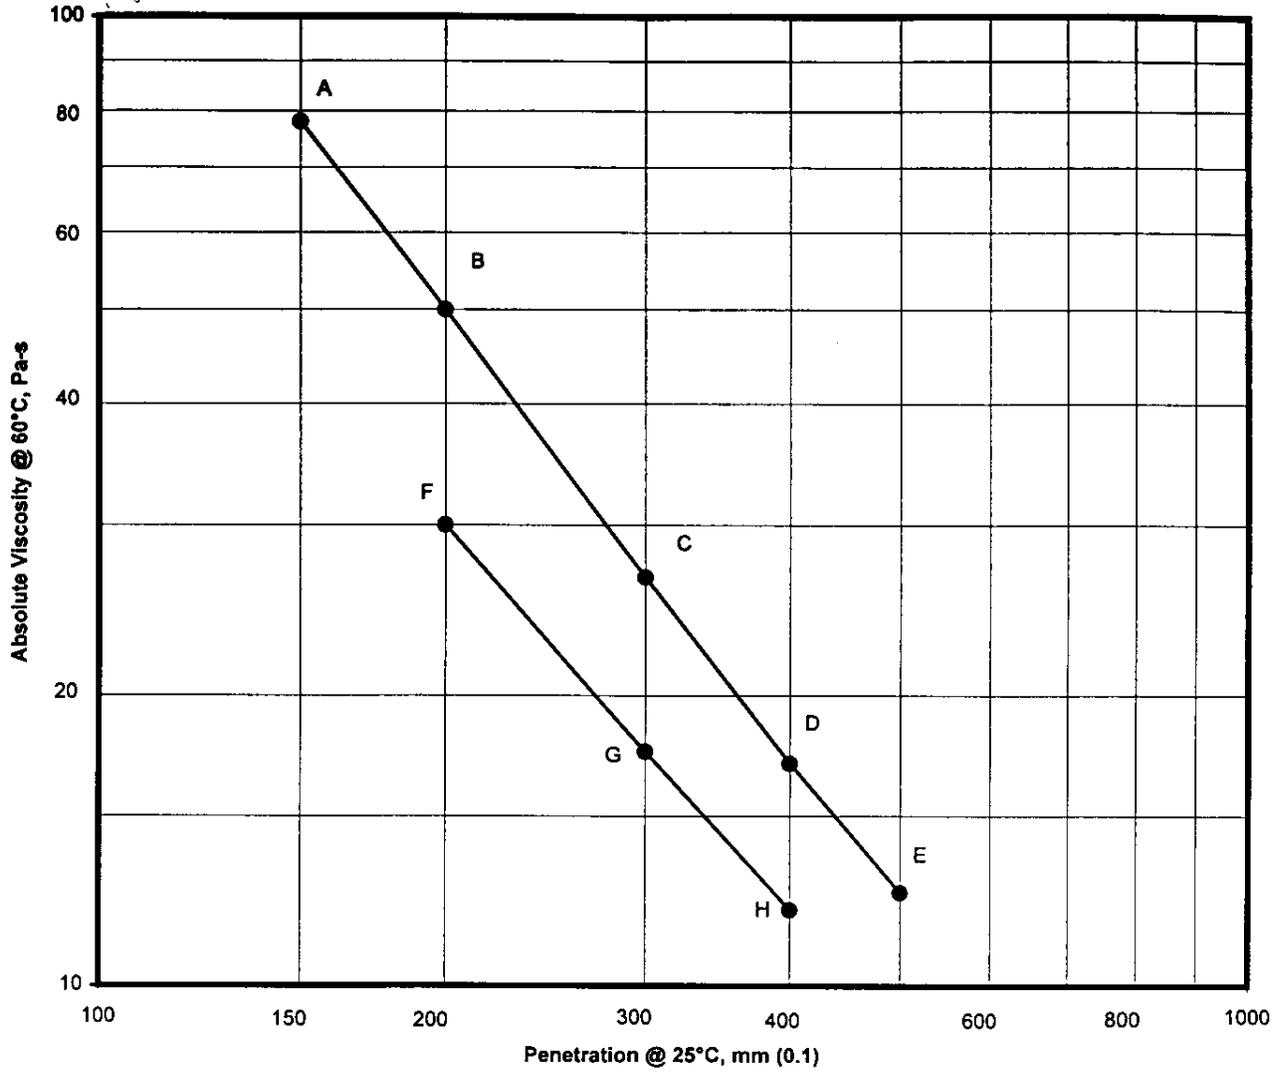

GRADE OF ASPHALT	150-200A			200-300A			300-400A			400-500A			200-300B			300-400B		
	POINT	ABS. VISC.	PEN.															
VISCOSITY & PENETRATION SHALL BE WITHIN GRAPHIC REGIONS DESCRIBED BY THE LETTERED CO-ORDINATES	A	78	150	B	50	200	C	26.5	300	D	17	400	B	50	200	C	26.5	300
	B	50	200	C	26.5	300	D	17	400	E	12.5	500	F	30	200	G	17.5	300
													G	17.5	300	H	12	400
													C	26.5	300	D	17	400

NOTE: THERE ARE NO MAXIMUM VISCOSITY LIMITS FOR "A" GRADE ASPHALT CEMENTS

Disclaimer: "To ensure the most accurate and current information, the specific agency should be contacted."

